


Energy, Environment and Storage

Journal Homepage: www.enenstrg.com

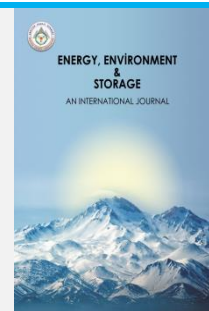

Tailoring Activated Carbon Surfaces: A Comparative Study of Nitric and Chlorosulfonic Acid Modifications

Betul Aykut-Senel¹, Cihan Ozgur², Sehnaz Sule Kaplan-Bekaroglu¹, Nuray Ates³

¹Suleyman Demirel University, Engineering Faculty, Department of Environmental Engineering, 0000-0003-3674-5525, 0000-0003-0917-7219

²Isarta University of Applied Sciences, Sutculer Prof. Dr. Hasan Gurbuz Vocational High School, 0000-0001-6085-1585

³Erciyes University, Engineering Faculty, Department of Environmental Engineering, 0000-0002-8923-4852

ABSTRACT. Surface modification approaches can improve the adsorbent's physicochemical characteristics, which are crucial to the effectiveness of the adsorption process. This study investigated the effects of chemical modification on the structural and chemical properties of four different powdered activated carbon (AC) samples. Surface modifications were performed using nitric acid and chlorosulfonic acid. The modified adsorbents were comprehensively characterized by Brunauer–Emmett–Teller (BET) surface area analysis, Scanning Electron Microscopy (SEM), Fourier Transform Infrared Spectroscopy (FTIR), and Dynamic Light Scattering (DLS). Additionally, the Boehm titration method was employed to evaluate the surface acidity and functional group composition. According to the research results, nitric acid modification led to a smoother and more uniform surface morphology and a more consistent pore size distribution compared to chlorosulfonic acid treatment. Nitric acid introduced functional groups such as $-\text{OH}$, $-\text{COOH}$, and $\text{C}=\text{C}=\text{C}$, while chlorosulfonic acid resulted in the incorporation of sulfonic groups ($\text{S}=\text{O}$ and SO_3H). Among the modified samples, AC4S exhibited the highest surface area ($868.48 \text{ m}^2/\text{g}$) and pore volume ($0.88 \text{ cm}^3/\text{g}$). The largest average particle size (1419.44 nm) was observed in the AC1S sample. While double modification increased particle size distribution, it negatively affected surface area and pore volume. Overall, the findings indicate that both nitric acid and chlorosulfonic acid modifications effectively tailor activated carbon's chemical and structural features, offering promising potential for adsorption-based applications.

Keywords: Activated carbon, adsorption, characterization, chemical modification, chlorosulfonic acid, nitric acid.

Article History: Received:xxx; Revised: xxxx; Accepted:xxx; Availableonline: xxx

1. INTRODUCTION

Achieving ecosystem balance and long-term sustainability necessitates research into removing micropollutants from water, particularly pesticides, pharmaceuticals, and personal care products present at very low concentrations ($\mu\text{g}/\text{L}$ – ng/L). Conventional treatment methods are inefficient enough to remove these pollutants from water [1]. Adsorption is one of the most promising advanced treatment technologies, especially for removing micropollutants, due to its high removal capacity, ease of application, and no toxic by-products [2]. The most significant disadvantage of the adsorption process is the need for regeneration [4]. This problem can be eliminated by using commercial powdered activated carbon (PAC) in the adsorption process.

Adsorption performance is generally evaluated according to the capacity and selectivity of adsorbents, and

considering this situation, adsorbent selection is an important factor in pollutant removal [3]. In the interest of environmental sustainability, high-performance materials like activated carbon are now needed for the adsorption of persistent organic and inorganic chemicals from water sources. In general, activated carbon (AC) is an amorphous type of carbon that can be produced from various carbon sources through either chemical or physical activation [5–7]. The material has several uses in various sectors due to its high surface area, porosity, advanced internal pore structure with micro, meso, and macro pores, and many functional groups on its surface [8].

Recent studies have further highlighted advances in AC modification, underlining both opportunities and limitations of current strategies [9]. In particular, nitric acid modification has recently been shown to enhance

adsorption efficiency for phenolic compounds and heavy metals [10]. The addition of different functional groups and/or structural modifications to ACs improves their characteristics by increasing their selectivity and capacity for adsorption of contaminants. Numerous methods have been examined in the literature, including chemical, biological, and physical change [11-13]. It is well known that these modified ACs enhance the adsorbent structure and boost the adsorption capacity [14-16].

Differences in the modification procedure and the type of modifying agent used directly impact how the AC adsorbs pollutants and how it works [17]. Therefore, choosing the proper modification technique is very important for the physicochemical structure of the AC. The specific surface area of the adsorbent can be increased, and surface functional groups, pore structures, and particle size distributions can be changed by AC modification. In particular, chemical modification techniques that use organic acids, hydrogen peroxide, and inorganic acids (such as hydrochloric, sulfuric, and nitric acids) successfully boost the quantity of surface functional groups [13, 18, 19].

Modifying AC with nitric acid resulted in functional groups with a high amount of accessible oxygen on the adsorbent surface in the studies conducted by Gökçe and Aktaş [20] and Valentin-Reyes et al. [21]. Following modification, Li et al. [22] found that groups like lactone and carboxyl enhanced the number of oxygen-containing groups on the AC's surface while also making the surface more hydrophilic. Wolak and Orzechowska-Zięba [13] claimed in their study that oxygen groups on the carbon surface are evident when polar adsorbates are adsorbed. In many studies using nitric acid as an oxidizer, it was observed that the modification positively affected the micropore and mesopore volume, increasing the adsorption capacity of pollutants [23-25]. Liu et al. [26] observed that the adsorption capacity of Cr (VI) increased from 7.61 mg/g to 13.74 mg/g due to AC modification with nitric acid. In another study, the increase in adsorption capacity from 24.86 mg/g with the original AC to 54.74 mg/g due to modification with nitric acid is an important result [27].

Recently, sulfonic acid modification, another technique that may raise surface acidity, has much promise [28]. Alvear-Daza et al. [29] reported that extreme acid sites were formed due to the effective incorporation of SO₃H compound into the structure by chlorosulfonic acid modification. When Goswami and Phukan [30] used sulfonic acid modification to remove dyes (RhB and Orange G), they found that the adsorption capacity rose from 318.5 mg/g to 757.6 mg/g.

Characterization of the adsorbent's properties is necessary to assess the effectiveness of the adsorption process and better understand it [31]. Various methods have been developed to characterize structural and physicochemical properties such as pore volumes, surface area, thermal stability, hydrophilicity, surface chemistry, functional groups of surfaces, pH, elemental analysis, water vapor adsorption, nitrogen adsorption, and moisture content [32]. Scanning electron microscopy (SEM), Transmission electron microscopy (TEM), N₂ adsorption/desorption isotherm, Fourier transform infrared spectroscopy (FTIR),

X-ray photoelectron spectroscopy (XPS), Boehm titration, Potentiometric titration, and zero charge point are some of the commonly used characterization techniques for adsorbents [33, 34].

In this paper, commercial powdered activated carbons, which are preferred for obtaining modified adsorbents, were modified with nitric acid and chlorosulfonic acid. In the literature searches, no recent study was found to compare commercial powdered AC's modification with nitric acid and sulfonic acid. The effect of double modification (steam+nitric acid, steam+sulfonic acid, chemical treatment+nitric acid, chemical treatment+sulfonic acid) was also investigated in this study. The effect of modification on adsorbent structures was elucidated by SEM, Brunauer, Emmet, and Teller (BET), FTIR, and dynamic light scattering (DLS) analysis. At the same time, the changes in surface chemistry were investigated by pH_{PZC} and surface acidic and basic groups experiments.

2. MATERIALS AND METHODS

2.1 Materials and chemicals

In the modification studies, four commercial PACs were used: Norit CA1 (Cat. No. 97876), Norit SX F Cat (Cat. No. 901933), AC Puriss (Cat. No. 31616), and Norit SX ULTRA (Cat. No. 53663). Chemical modification was done to Norit CA1, and steam modification was done to Norit SX ULTRA. The four different types of PAC are original ACs purchased from Sigma-Aldrich. The general characteristics of the ACs are presented in Table 1. The concentrated nitric acid (specific gravity 1.43 g/m³, 65% purity) used for modification was high-purity and supplied by Merck. Purchased from Sigma-Aldrich were hydrochloric acid (specific gravity 1.19 g/m³, 37% purity) and chlorosulfonic acid (ClSO₃H), with a specific gravity of 1.48 g/m³, 99% purity.

Table 1. Properties of Commercial Adsorbents Used in Modification Experiments

Adsorbents	Surface Area (m ² /g)	Pore size	Density (g/ml)
Norit CA1	1400	Macro/Meso	0.9
Norit SX ULTRA	1200	Micro/Meso	0.743
Norit SX F Cat	750	Micro/Meso	1.8 – 2.1
AC Puriss	300	Micro/Meso	1.8 – 2.1

2.1.1 Nitric acid modification of activated carbons

In the nitric acid modification of PACs, the method of Guha et al. [35] was modified and applied. Before modification, the adsorbents were cleaned with deionized and distilled water and dried at 105 °C in an oven.

Five steps were used to modify the dried activated carbons. Summary of the five-step modification process:

1. HCl Pre-treatment: The activated carbon is treated with 2.5 M HCl at 120 °C for 18 hours to remove impurities.

2. Boiling in Water: The sample is boiled in pure water at the same temperature for 8 hours to purify it further.

3. Nitric Acid Modification: The AC is treated with 7 M HNO₃ at 120 °C for 16 hours to introduce functional groups that can enhance adsorption.

4. Washing: The modified AC is washed with distilled and deionized water until a constant pH of ~5-6 is achieved.

5. Drying: Ultimately, a vacuum oven is used to dry the AC at 60-70 °C for about 48 hours until a constant weight is reached, indicating complete drying.

The 40% weight loss during washing is significant, as it reflects the removal of soluble impurities and possibly some of the carbon structure. The resulting modified activated carbons are labeled as ACN (*Table 2*).

2.1.2 Chlorosulfonic acid modification of activated carbons

The technique used by Goswami and Phukan [30] in their study was adapted and used to modify PACs using sulfonic acid. It was carried out in 5 steps. Each step of the method is clearly summarized below.

1. Preparation of Activated Carbon:

Washing: Deionized and distilled water were used to wash the activated carbons.

Drying: 105 °C in an oven to dry.

2. Dichloromethane Treatment:

Weighing: 30 grams of activated carbon were weighed.

Solution Preparation: 900 mL of dichloromethane (CH₂Cl₂) was added.

Ultrasonic Bath: Stirred for 45 minutes.

Cooling: Cooled using ice molds.

3. Chlorosulfonic Acid Addition:

Dropwise Addition: 30 mL of chlorosulfonic acid was added dropwise over 30 minutes at room temperature.

Shaking: The mixture was agitated for an additional 3 hours to ensure complete dispersion of the acid.

4. Filtration and Washing:

Filtration: The final product was filtered.

Washing: Washed with ethanol and water.

5. Final Drying:

Drying: Dried at 80 °C until a constant weight was achieved.

Storage: The dried activated carbons were stored in a desiccator.

Final Product: The modified activated carbons were labeled as ACS (*Table 2*).

Table 2 Properties and Codes of Original and Modified Adsorbents

Adsorbents	Codes	Properties
Norit SX ULTRA	AC1	Peat-Based, Steam-Modified, High Purity, Powder Form
Norit CA1	AC2	Wood-Based, Chemically Modified, Powder Form
Norit SX F Cat	AC3	Original
AC Puriss	AC4	Original
Norit SX ULTRA	AC1N	Steam + Nitric Acid Modification
Norit CA1	AC2N	Chemical + Nitric Acid Modification
Norit SX ULTRA	AC1S	Steam + Sulfonic Acid Modification
Norit CA1	AC2S	Chemical + Sulfonic Acid Modification
Norit SX F Cat	AC3N	Nitric Acid Modification
Norit SX F Cat	AC3S	Sulfonic Acid Modification
AC Puriss	AC4N	Nitric Acid Modification
AC Puriss	AC4S	Sulfonic Acid Modification

2.2 Characterization techniques

2.2.1 pH_{PZC} analysis

The neutral charge point (pH_{PZC}, the pH value at which the total net surface charge is zero) and the ability to neutralize acids and bases define the surface chemistry of adsorbents. The pH_{PZC} values of activated carbon samples were determined by the pH equilibration method [36]. By adding 0.5 M HCl and/or 0.5 M NaOH, the pH values of the 0.1 M NaCl solution produced in distilled water were brought to pH 2-12. From these solutions, 20 ml of samples were taken in 25 ml amber sample bottles, and 100 mg of adsorbent was added. Adsorbent-free control samples were also made for every pH level. The prepared samples were shaken for 48 hours at 20±5 °C and 100 rpm. Following the mixing time, the samples were allowed to settle for an hour before their pH levels were determined. The pH_{PZC} value is the same pH value that does not change after 48 hours of contact. Nonetheless, interpolation is typically necessary to determine the pH_{PZC} value precisely. The effect of acid modification on the adsorbent's net surface charge was ascertained by noting the pH_{PZC} values of the original and modified activated carbons, which remained consistent over 48 hours.

2.2.2 Total surface acidic and basic values of adsorbents

The Boehm technique (alkalimetric titration) was used, with some slight adjustments, to quantify the total surface acidic groups (NaOH adsorption) and total surface basic groups (HCl adsorption) [36]. 20 ml of 0.05 N NaOH or 0.05 N HCl solution was added to 25 ml bottles containing

200 mg of adsorbent each. Control samples without adsorbent were also prepared with the samples. For 48 hours at room temperature, the prepared samples were agitated at 100 rpm. After the specified period of time, the samples were left for an hour to allow the adsorbents to settle before being filtered. Considering pH variations, 10 mL of the filtered samples were used in the titration procedure. The final stage was titrating the solution with 0.05 N HCl using 0.05 N NaOH. The total number of surface basic groups was determined by comparing the quantity of NaOH absorbed by the control sample with that of the sample that included the adsorbent. To find the total number of acidic groups on the surface, 0.05 N HCl was used to titrate the sample that contained 0.05 N NaOH. The total surface acidic groups were calculated by using the amount of HCl consumed for the sample containing the adsorbent and the control sample.

2.2.3 Surface area measurement (BET) analysis

The Micromeritics Gemini VII Surface Area and Porosity Surface Analyser was used to measure the adsorbents' surface areas and total pore volumes. N₂ adsorption-desorption isotherms were used to determine the surface area of adsorbents. BET analyses were carried out at Erciyes University Technology Research and Application Centre.

2.2.4 Scanning electron microscope (SEM) analysis

SEM analyses of the original and modified adsorbents were carried out at Erciyes University Nanotechnology Research Centre. Using a Zeiss Evo LS10 scanning electron microscope (SEM), the surface morphology of the adsorbents was reviewed.

2.2.5 Fourier transform infrared spectrometry (FTIR-ATR) analysis

FTIR analyses provide information at the molecular level about new functional groups added to the surface or changes on the surface due to surface modification processes. FTIR analyses of the original and modified adsorbents were measured in the wavelength range of 400-4000 cm⁻¹ by a Perkin Elmer 400 FT-IR/FT-FIR device at Erciyes University Technology Research and Application Centre.

2.2.6 Particle size distribution analysis

The dynamic light scattering (DLS) technique was used to determine the particle size distribution of the original and modified activated carbons. A Malvern NanoZS90 device with a 633 nm laser was used to perform DLS measurements at room temperature. A scattering angle of 173° was used to acquire the data.

Dimensional analyses were performed at Erciyes University Nanotechnology Research Centre on a retainer basis.

3. RESULTS AND DISCUSSIONS

3.1 SEM Analyses

SEM analysis is a method for determining the physical characteristics and surface morphology of the materials being studied. The adsorbents modified by nitric acid and sulfonic acid are shown in Figure 1 as SEM images with a size of 2 µm and a magnification scale of 500 KX. Upon examining the AC1 and AC2 adsorbents prior to modification, they exhibit an extensive particle size distribution, containing very small, activated carbon granules within their structure. Post nitric acid modification, both adsorbents (AC1N, AC2N) appear more homogeneous in terms of size. During the nitric acid modification, repeated washing of activated carbon with acid and pure water results in the removal of the smaller activated carbon particles.

Consequently, as evidenced by the SEM images of AC1N and AC2N adsorbents, larger and cleaner activated carbon granules remain. This characteristic is attributed to the modification process's cleansing impact. A similar observation was reported by Ge et al. [37], who noted that the surface of the modified adsorbent was cleaner and the surrounding pores smoother. Additionally, literature reports indicate that post-nitric acid modification, activated carbon forms a smoother, more uniform, and narrow-pored structure, supported by a reduction in BET surface area [25, 38, 39]. The SEM images of AC1N and AC2N adsorbents also corroborate the low surface area obtained from the BET analysis results. Moreover, several investigations in the literature have documented that nitric acid treatment may considerably impact activated carbon's physical shape [40-42].

Upon examining the SEM images of the AC3N and AC4N adsorbents, it is observed that a clean and smooth structure similar to that of other adsorbents has formed. Lu et al. [14] noted that the surface morphology of adsorbents activated with coconut exhibited a clean and eroded appearance due to the oxidation by nitric acid. Unlike the other adsorbents, the AC3 and AC4 adsorbents showed a significant increase in surface area as a result of nitric acid modification. This is attributed to the fact that AC3 and AC4 are original (untreated) adsorbents, while AC1 and AC2 are pre-treated adsorbents. It was concluded that modifying untreated adsorbents with nitric acid positively impacts the surface area. According to Su et al. [25], mass transfer during adsorption was facilitated by creating new pores following nitric acid modification, which expanded the contact area.

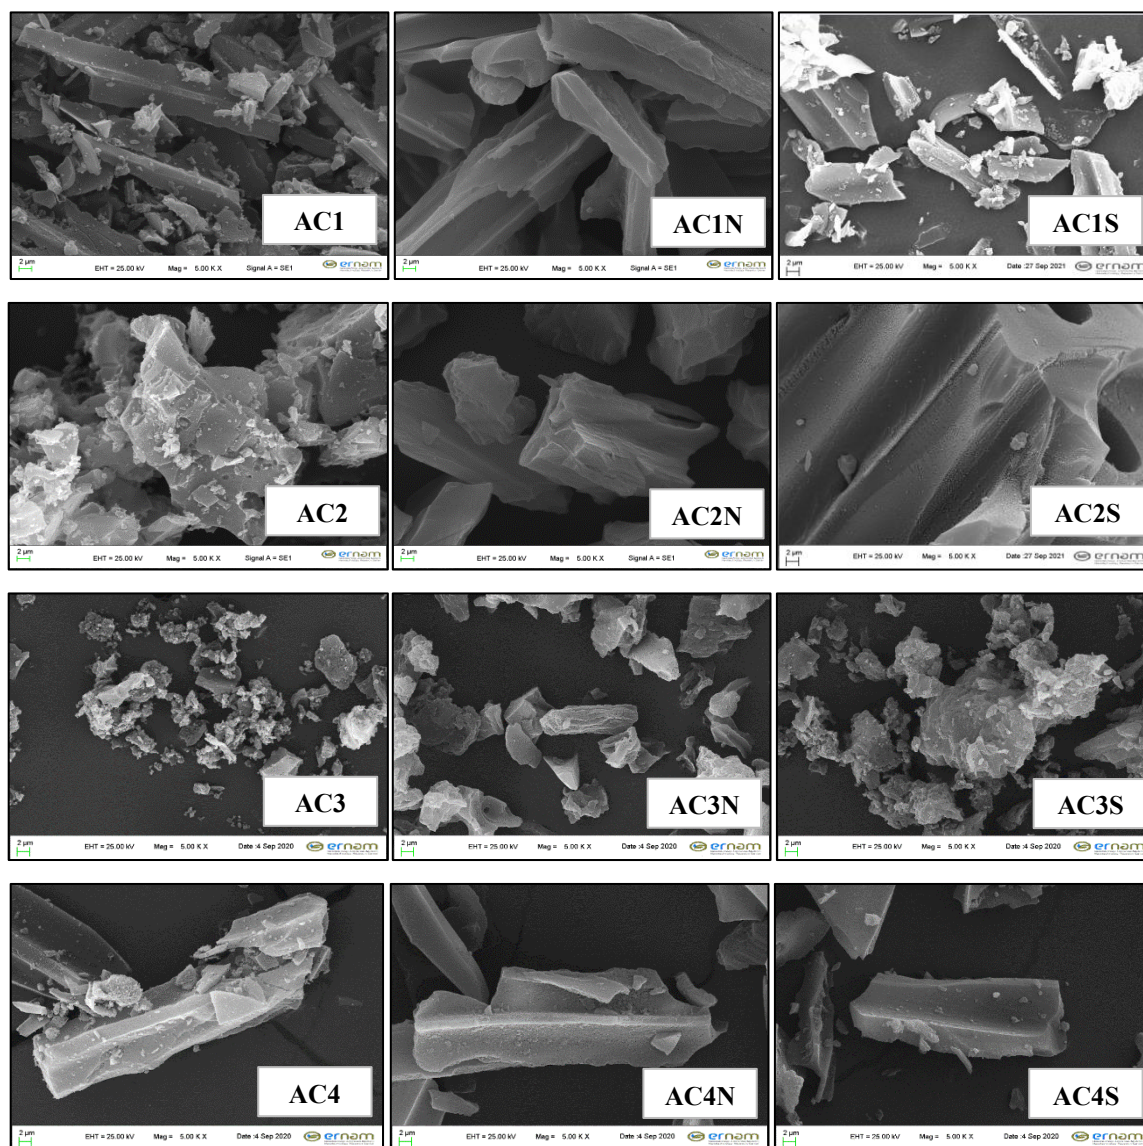


Fig. 1 SEM images of original and modified ACs (2 μm mag: 500 KX)

3.2 FTIR Analyses

Figure 2 shows the FTIR spectra of the original and modified AC1 and AC2 adsorbents. In the FTIR spectrum of the AC1 adsorbent, bands observed at 2987.3 cm^{-1} and 2899.6 cm^{-1} are attributed to the aliphatic $\nu(\text{C-H})$ stretching in the $-\text{CH}-$ bond found in the aromatic methoxyl group and the side chains of methyl and methylene groups [43]. Both symmetric and asymmetric C-H vibrations are linked to bands seen roughly between 2950 and 2800 cm^{-1} , suggesting the existence of aliphatic compounds [44]. The band in the range of $1800\text{--}1300\text{ cm}^{-1}$ is characteristic of highly conjugated C=O stretching and C-O structures [45]. The peak at 1407.2 cm^{-1} is attributed to the C=O stretching vibration of carboxylic acid or ketone. The presence of peaks at 1080 and 1300 cm^{-1} in the AC1 spectrum can be associated with the C-O stretching vibrations of carboxylic acids, phenols, alcohols, or esters [30]. The FTIR spectra for AC1 reveal that the modification with HNO_3 resulted in significant chemical changes in the structure of AC1N, with the disappearance of many bands. There are just two prominent peaks in the modified AC1N spectrum, which may be linked to the allen ($\text{C}=\text{C}=\text{C}$) group. Another band around 2100 cm^{-1} , relatively broad, is also attributed to the allen ($\text{C}=\text{C}=\text{C}$) group [46-47].

In the FTIR spectrum of the AC2 carbon, the peaks at 2986.9 cm^{-1} and 1987.6 cm^{-1} disappeared after nitric acid modification. The 2099.2 cm^{-1} band in the AC2 sample slightly increased after modification, forming the 2111.5 cm^{-1} band. This relatively broad peak around 2100 cm^{-1} is attributed to the allen ($\text{C}=\text{C}=\text{C}$) group [46-47]. The presence of carboxyl groups produced by nitric acid is shown by the signal in the AC2N sample at 1707 cm^{-1} [8]. Similarly, Schepetkin et al. [48] observed a strong absorbance in the $1650\text{--}1720\text{ cm}^{-1}$ band, which they attributed to $-\text{COOH}$ group vibrations. Another study associated the peak at 1729 cm^{-1} with the specific peak of the C=O bond stretching vibrations in the carboxylic acid functional group [49]. Shim et al. [50] reported an increase in adsorption bands in the $1750\text{--}1400\text{ cm}^{-1}$ range for carboxylic acid and quinone groups when comparing the spectra of activated carbon fibers modified with HNO_3 to general spectra.

The bands observed between $1500\text{--}1600\text{ cm}^{-1}$ in both spectra of AC2N and AC2S originate from C=C stretching vibrations in the quinone and keto-enol aromatic rings [51]. According to the FTIR data, oxidation with HNO_3 produces several surface functional groups, including quinone, carboxyl, and carbonyl. Following activated carbon activation, certain functional groups persisted while others were destroyed or new functional groups were created, according to an analysis of the FTIR spectrum.

This observation aligns with the literature, confirming the presence of observed functional groups for AC2N in our experiments [52]. New peaks appeared at 3791 cm^{-1} and 3483 cm^{-1} in AC1S carbon and 3289.8 cm^{-1} in AC2S carbon. These peaks around 3300 cm^{-1} correspond to the $-\text{OH}$ group [53]. S-O stretching vibrations are attributed to new peaks observed at 611.24 cm^{-1} and 530.62 cm^{-1} in AC2S adsorbent [30].

Figure 3 presents the FTIR spectra of original and modified AC3 and AC4 activated carbons. The original AC3 carbon structure includes 2314 , 2103 , 2000 , and 585.44 cm^{-1} bands. Nitric acid modification caused the bands at 2103 and 2314 cm^{-1} to widen, and peaks at 2355 and 2116 cm^{-1} to emerge. After nitric acid modification, the 585.4 cm^{-1} band disappeared, and a peak was observed at 576.8 cm^{-1} . Upon examining the FTIR spectrum of AC4 and nitric acid-modified AC4N carbon, it was observed that the band at 3793 cm^{-1} disappeared after nitric acid modification, replaced by a peak at 3564 cm^{-1} . Peaks in the approximately $3700\text{--}3500\text{ cm}^{-1}$ range are attributed to $-\text{OH}$ groups [30].

The broad and strong band observed between $3655\text{--}3000\text{ cm}^{-1}$ after both modifications is attributed to the stretching vibration of $\nu(\text{O-H})$ from adsorbed water or functional groups on the surface [43]. The sulfonic acid modification of the original AC3 carbon resulted in a peak at 1058.4 cm^{-1} corresponding to the S=O structure in AC3S carbon. Similarly, Huang et al. [54] associated peaks between $1030\text{--}1100\text{ cm}^{-1}$ with sulfonic structures. Following sulfonic acid modification, the band at 3793 cm^{-1} in the spectra of AC4 carbon vanished, and a band replaced this at 3560.3 cm^{-1} in the spectrum of AC4S carbon. Additionally, a new band at 1993.6 cm^{-1} was observed in AC4S, indicating functionalization of the adsorbent surface with S=O and SO_3H groups. Similarly, Kamari et al. [55] associated peaks with the S=O groups and SO_3H group OH stretching absorption roughly between 1649 and 2900 cm^{-1} . Double-bonded C=O groups are responsible for the peaks in the AC4S carbon spectrum that are seen between 2100 and 2400 cm^{-1} [41]. At some point, the findings show that, depending on the properties of the targeted contaminants, activated carbon functionalized with sulfonic acid can be employed in adsorption investigations with good results.

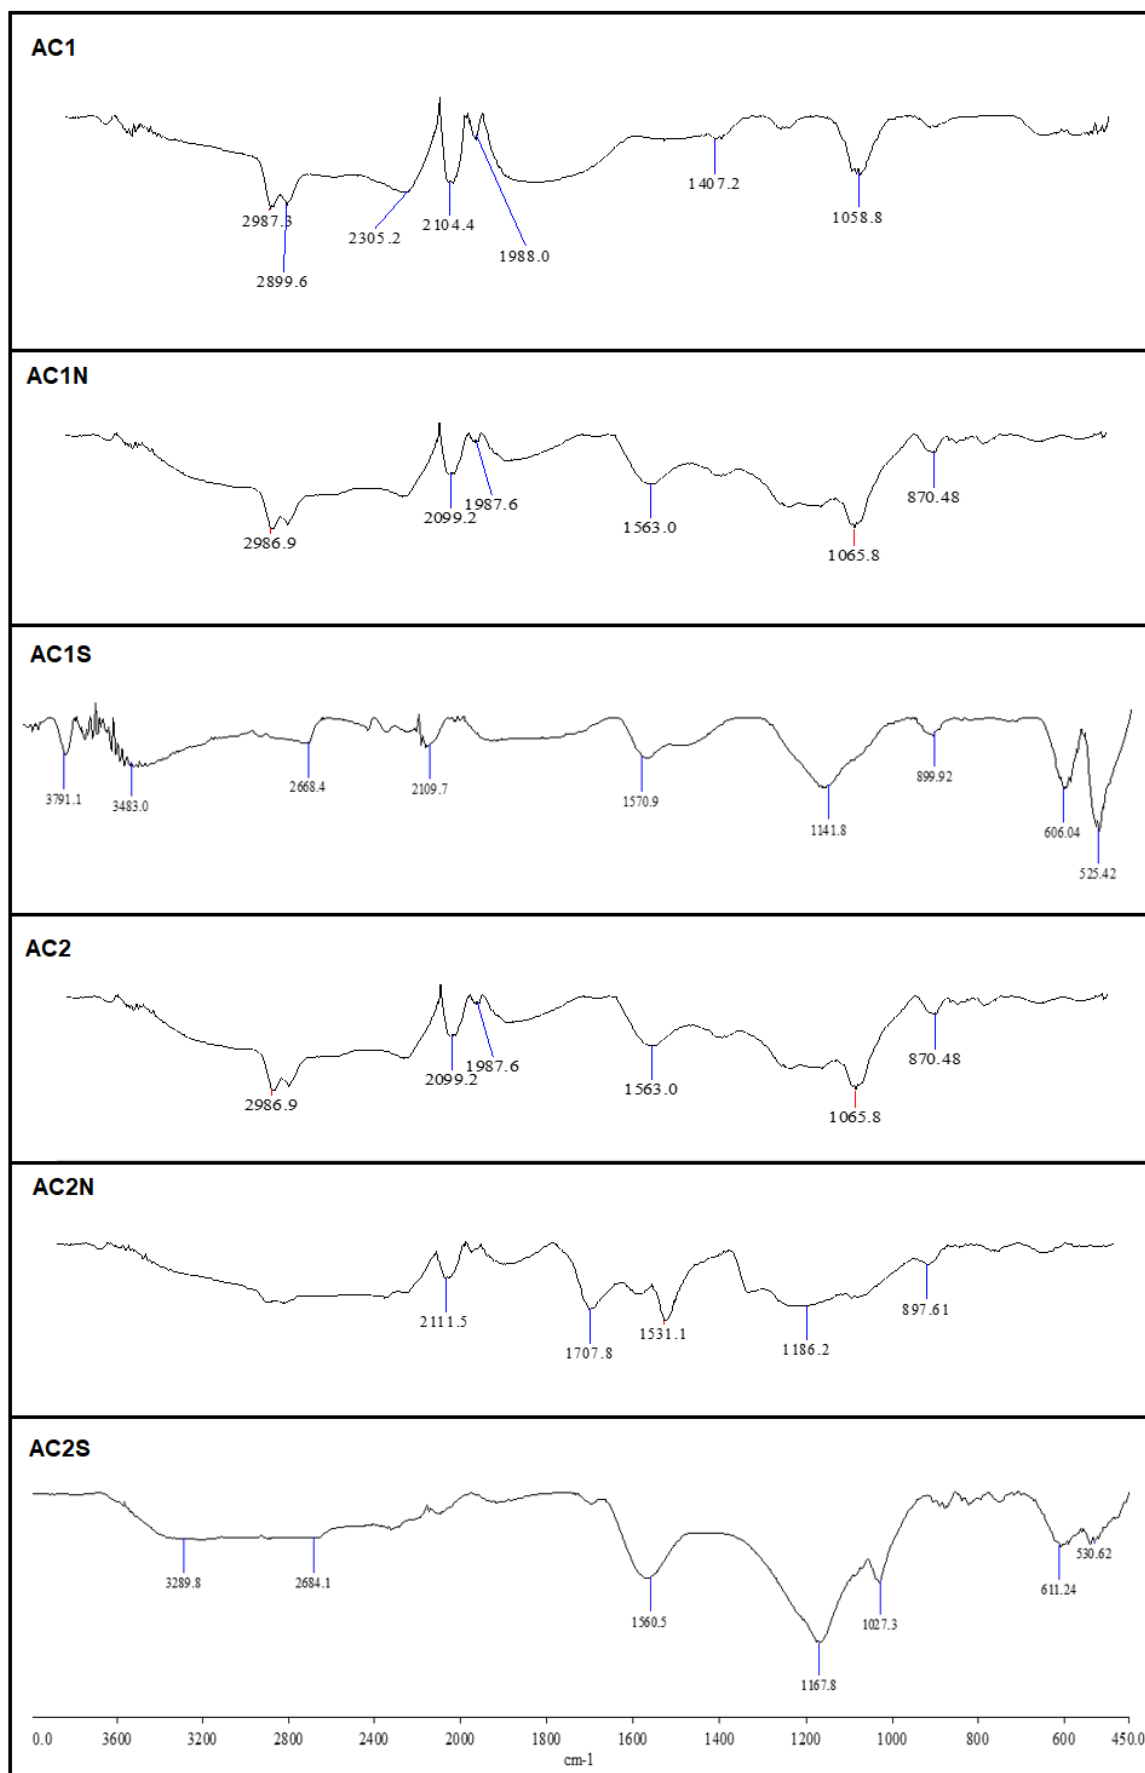


Fig. 2 FT-IR spectra of original and modified AC1 and AC2 activated carbons.

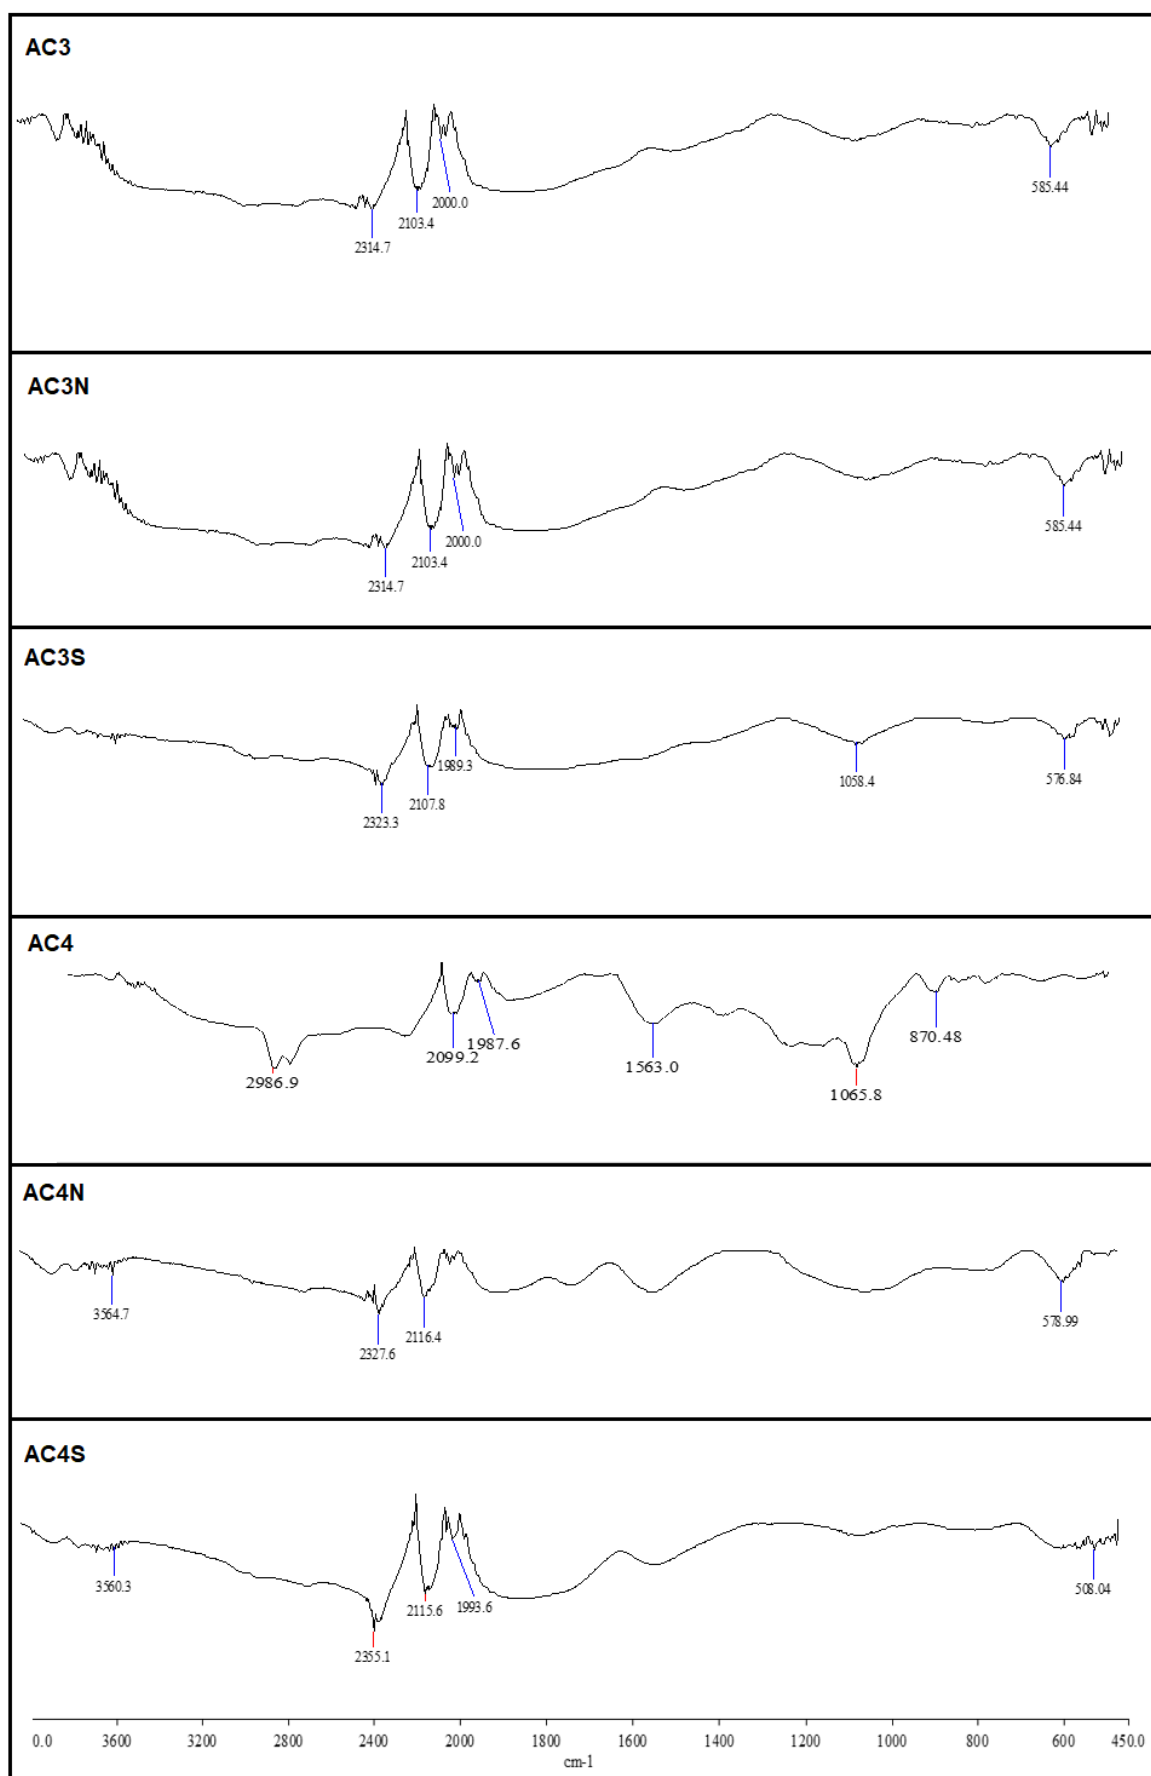


Fig. 3. FTIR spectra of original and modified AC3 and AC4 activated carbons.

3.3 BET Surface Area, Pore Volume, and Pore Size Analysis Results

N₂ adsorption-desorption isotherms were used to explain how modifications affected surface area and pore characteristics. The pore structure properties obtained from these isotherms are provided in Table 3. Table 2 shows how nitric acid and sulfonic acid modifications affected the activated carbon samples' structural properties abundantly. Each modification agent can cause significant and distinct changes in the adsorbent structure, underscoring the importance of understanding the behavior of each agent (nitric and sulfonic acid). BET analysis based on nitrogen gas adsorption at 77 K revealed changes in surface area and porosity measurements as a result of both modifications. Nitric acid modification caused a decrease of 39% and 76% in the surface areas of AC1 and AC2 adsorbents, respectively. There are two potential implications that many researchers attribute to this observation: The first is the partial breakdown of microporous walls [56, 57], and the second is the obstruction of pore entrances due to the development of oxygen functional groups [58]. The observed decrease in BET surface area following nitric acid modification can be attributed to the collapse of micropore walls or the blockage of pore entrances due to the formation of oxygen-containing functional groups, which reduce the accessible surface area for adsorption. Conversely, other studies interpret the increase in surface area after nitric acid treatment as dissolution of ash and opening of some blocked pores in activated carbon, ShamsiJazeyi and Kaghazchi [49], which was observed as a 30% increase only in AC3N adsorbent. In contrast, after sulfonic acid modification, AC3 showed a slight decrease in surface area, whereas AC4 exhibited a significant increase from 273.56 m²/g to 868.48 m²/g.

Total pore volume is another significant characterization outcome. Nitric acid modification resulted in a trend of pore loss in all adsorbents except AC3N and AC4N. The decrease in pore volume, similar to the decrease in surface area, has been attributed to the blocking of pores by oxygen functional groups due to chemical modification [59]. Yu et al. [60] investigated changes in carbon structure after oxidation with HNO₃ at different temperatures. They reported significant destruction of pore structure in commercially modified activated carbon samples compared to other AC samples, which they associated with the strong oxidative power of concentrated HNO₃ at 120°C. In our study, the modification with HNO₃ was also conducted at 120°C, aligning our results with findings in the literature. The decreasing trend in nitric acid modification was followed by an increasing trend in sulfonic acid modification. The overall pore volume of AC4 in the AC4S sample rose significantly, from 0.22 cm³/g to 0.88 cm³/g. Due to sulfonic acid modification, the adsorbents AC1S and AC2S saw a reduction in total pore volume. Specifically, the reduction from 1.12 cm³/g to 0.48 cm³/g in AC2S is notable, indicating that repeated sulfonic acid modification may lead to structural degradation, decreasing surface area and pore volume.

Table 3 Pore Structure Characterization of Original and Modified Activated Carbon Samples

Adsorbent	BET Surface Area (m ² /g)	Total Pore volume (cm ³ /g)	Pore Diameter (nm)
AC1	1200	0.95	3.16
AC2	1161	1.12	3.85
AC3	656.6	0.78	4.74
AC4	274	0.22	3.24
AC1N	732	0.52	2.85
AC2N	273.56	0.22	3.24
AC3N	855.05	0.85	3.98
AC4N	822.48	0.76	3.71
AC1S	929.93	0.61	2.62
AC2S	500.59	0.48	3.81
AC3S	635.61	0.78	4.91
AC4S	868.48	0.88	4.18

SBET: Surface area calculated using the Brunauer-Emmett-Teller (BET) theory, Pore diameter: adsorption average pore width (BET 4V/A)

Pore diameters can improve the removal capacity for pollutants that notably target pore sizes, and they are a greater driver of activated carbon performance than total surface area alone [61]. Typically, activated carbons have three pore classifications: macropores larger than 50 nm, mesopores ranging from 2 to 50 nm, and micropores smaller than 2 nm. Both original and modified adsorbents in this study exhibit mesoporous structures ranging from 2 to 5 nm. Following nitric acid modification, the pore sizes in all samples decreased. During nitric acid modification, some mesopores were blocked, leading to a reduction in mesopore volume as shown in Table 3. Numerous research investigations have documented that adding HNO₃ to activated carbon decreases its BET surface area, pore volume, and pore [20, 43, 62]. In contrast, sulfonic acid modification increased pore sizes. For instance, after modification, the original AC4 adsorbent had a pore width of 3.24 nm, which increased to 4.18 nm. These results indicate that nitric acid and sulfonic acid modifications alter the surface properties of activated carbons, affecting pore sizes in particular. However, the high temperature requirement, extended treatment time, and the mass loss observed during the washing step may impose certain limitations regarding practical applicability and scalability. This indicates that while the methods are effective at the laboratory scale, additional optimization may be required for industrial applications. In addition, the heterogeneous trends in surface area changes observed among the samples may be attributed to differences in the pre-treatment history of the commercial carbons. Furthermore, the consistently adverse outcomes of double modification highlight the need for future studies to identify an optimal single-modification strategy to achieve improved adsorption performance

3.4 pH_{PZC} , Surface Acidity and Basicity

Surface acidity or basicity is an important criterion defining the surface chemistry of activated carbon adsorbents. Carboxyl, lactone, phenolic hydroxyl, quinone, and carboxylic anhydride groups are common oxygen-containing functional groups found on the surface. It has been noted that the higher the oxygen content, the more acidic the surface [20]. Surface basicity, on the other hand, is associated with oxygen-free Lewis sites at the edges of carbon layers, carbonyls, pyrone, and chromene-type structures [37]. The pH_{PZC} findings and Boehm titration total acidic-basic groups are displayed in Table 4. Titration results indicate an increase in the total acidity of the activated carbon surface after nitric acid and sulfonic acid modifications. Notably, after nitric acid modification, an increase in total acid groups (meq/g) was observed for AC2 and AC4 adsorbents.

Gokce and Aktas [20] noted that higher initial concentrations of HNO_3 lead to increased formation of carboxylic groups on the surface, promoting the likelihood of carboxylic and phenolic groups co-locating and supporting lactonic group formation. However, some basic surface functional groups can be removed from the structure at high concentrations. These changes are typical outcomes of oxidative modifications observed frequently in previous studies [50, 63], where oxidative effects of HNO_3 during modification also result in reductions of basic surface functional groups.

Table 4 Data Obtained from the Boehm Method and Zero Point of Charge

Adsorbent	pH_{PZC}	Total Acidic Groups		Total Basic Groups	
		(meq/g)	(meq/m ²)	(meq/g)	(meq/m ²)
AC1	8.11	3.6	0.003	3.33	0.003
AC2	2.53	4.0	0.003	3.03	0.003
AC3	7.8	3.5	0.005	3.80	0.006
AC4	7.09	3.8	0.014	3.90	0.014
AC1N	2.08	4.1	0.006	3.00	0.004
AC2N	2.01	4.9	0.018	2.90	0.011
AC3N	2.88	3.950	0.005	3.725	0.004
AC4N	2.92	4.775	0.006	3.675	0.004
AC1S	4.98	3.05	0.0033	4.50	0.0048
AC2S	2.90	3.35	0.0067	4.30	0.0085
AC3S	2.9	3.950	0.006	3.650	0.006
AC4S	2.95	3.900	0.004	3.725	0.004

The number of basic sites generally decreases as a result of HNO_3 modification. This can be attributed to nitric acid's ability to neutralize or even eliminate basic sites [64]. In the case of sulfonic acid modification, as observed in Table 4, there is a slight increase in total acid groups while a decrease in basic groups occurs. The most notable decrease

was measured in AC4 adsorbent, which decreased from 0.014 meq/m² to 0.004 meq/m² in AC4S adsorbent. The adsorption capacity of contaminants in aqueous solutions is influenced by the pH at which the surface of the adsorbent becomes positively or negatively charged, as shown by measurements of pH_{PZC} [65]. The pH equilibrium technique was used to determine the adsorbents' pH_{PZC} values [36]. All modified carbons were observed to have lower PZC values compared to the original carbon samples. This indicates that acidic properties are dominant due to the modification process and that there are more weak acidic functional groups compared to others.

The adsorbent with the least change in pH_{PZC} value is AC2, which decreased from 2.53 to 2.01 after modification to AC2N. On the other hand, despite a slight decrease in pH_{PZC} value after modification for AC2, a significant increase in total acidic groups was observed. This phenomenon is associated with the strong oxidative effect of nitric acid modification. For AC3, AC4, and AC1 samples modified with sulfonic acid, a decreasing trend in pH_{PZC} values was observed. However, for AC2, sulfonic acid modification resulted in a slight increase in pH_{PZC} value from 2.53 to 2.90. Similarly, in a dye adsorption study by Goswami and Phukan [30], the pH_{PZC} values were reported as 5.18 for activated carbon (MTLAC) and 2.4 for sulfonic acid-modified activated carbon (MTLAC-SA).

3.5 DLS Analyses

Based on the DLS histograms, the changes in particle size distributions of original and modified adsorbents were determined using the weight average calculation method. Particle size analysis graphs of original and modified AC1 and AC2 adsorbents are presented in Figure 4. The x-axis in the graphs represents the particle size diameter in nm, and the y-axis indicates the percentage of particles by number. Upon examining the DLS histogram of the AC1 sample, it is observed to have a broad particle distribution ranging from 190.1 nm to 1718 nm. According to the weight average calculation method, the majority of the AC1 carbon is sized at 377.52 nm. After nitric acid modification, the particle size distribution of AC1N adsorbent was reduced, with an average size of 241.23 nm. The AC1S sample has an average particle size distribution calculated as 1419.44 nm. This suggests that the modification significantly increased particle size for AC1S carbon. Similarly, the average size distribution of AC2 adsorbent is 685.37 nm, whereas after nitric acid modification, AC2N adsorbent showed a significant decrease with an average size distribution of 259.66 nm. However, compared to AC1S, the average particle size distribution of the AC2S adsorbent decreased after sulfonic acid alteration, measuring 428.42 nm.

Particle size analysis graphs of original and modified AC3 and AC4 adsorbents are presented in Figure 5. The average particle size distributions of AC3 and AC4 adsorbents are calculated as 939.94 nm and 313.32 nm, respectively.

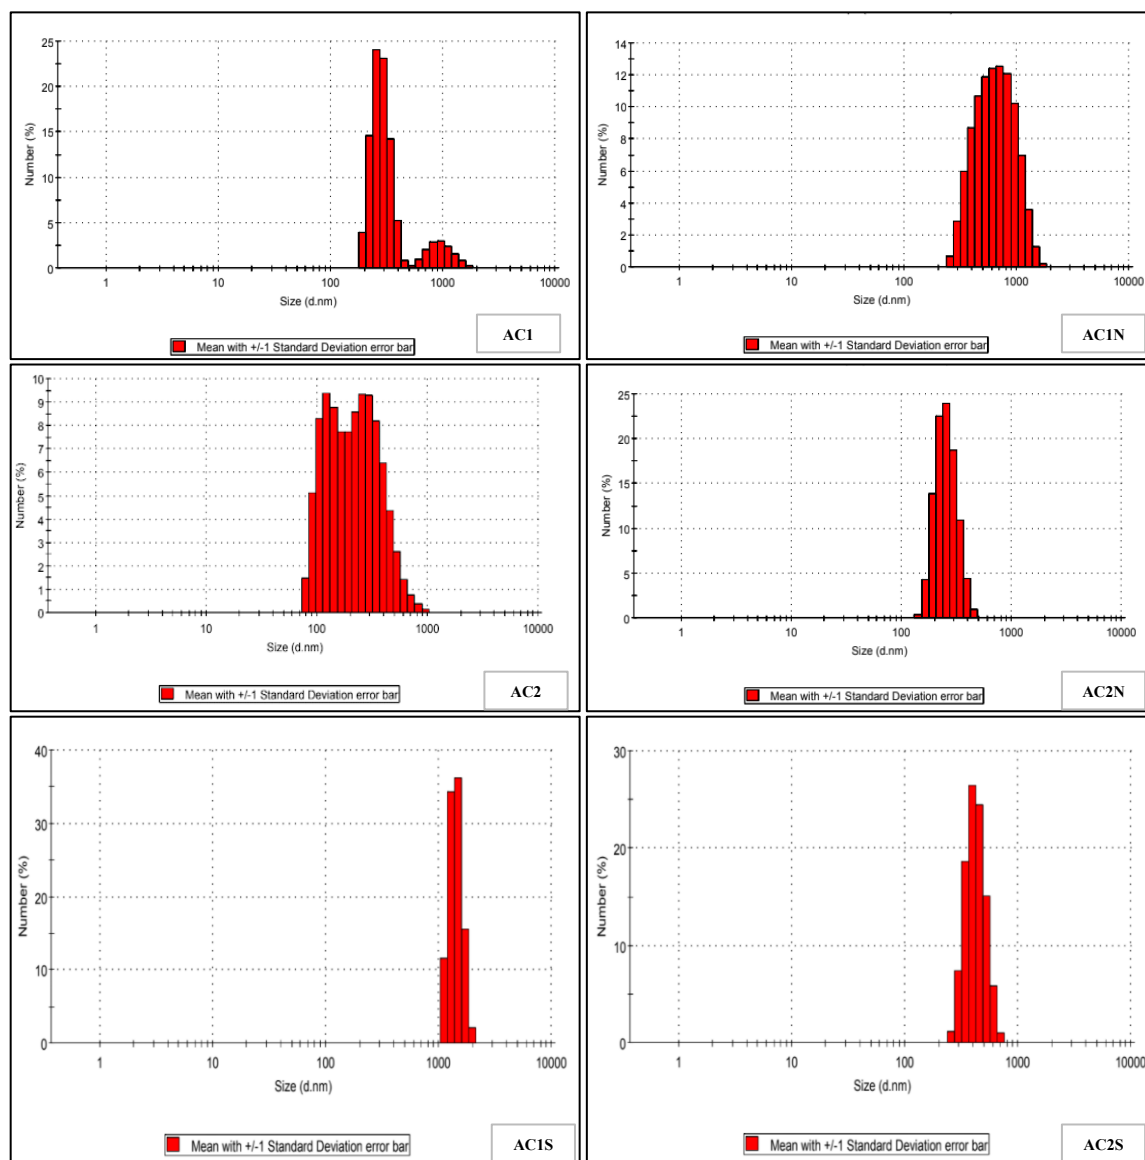


Fig. 4 Particle size analysis graphs of original and modified AC1 and AC2 activated carbons.

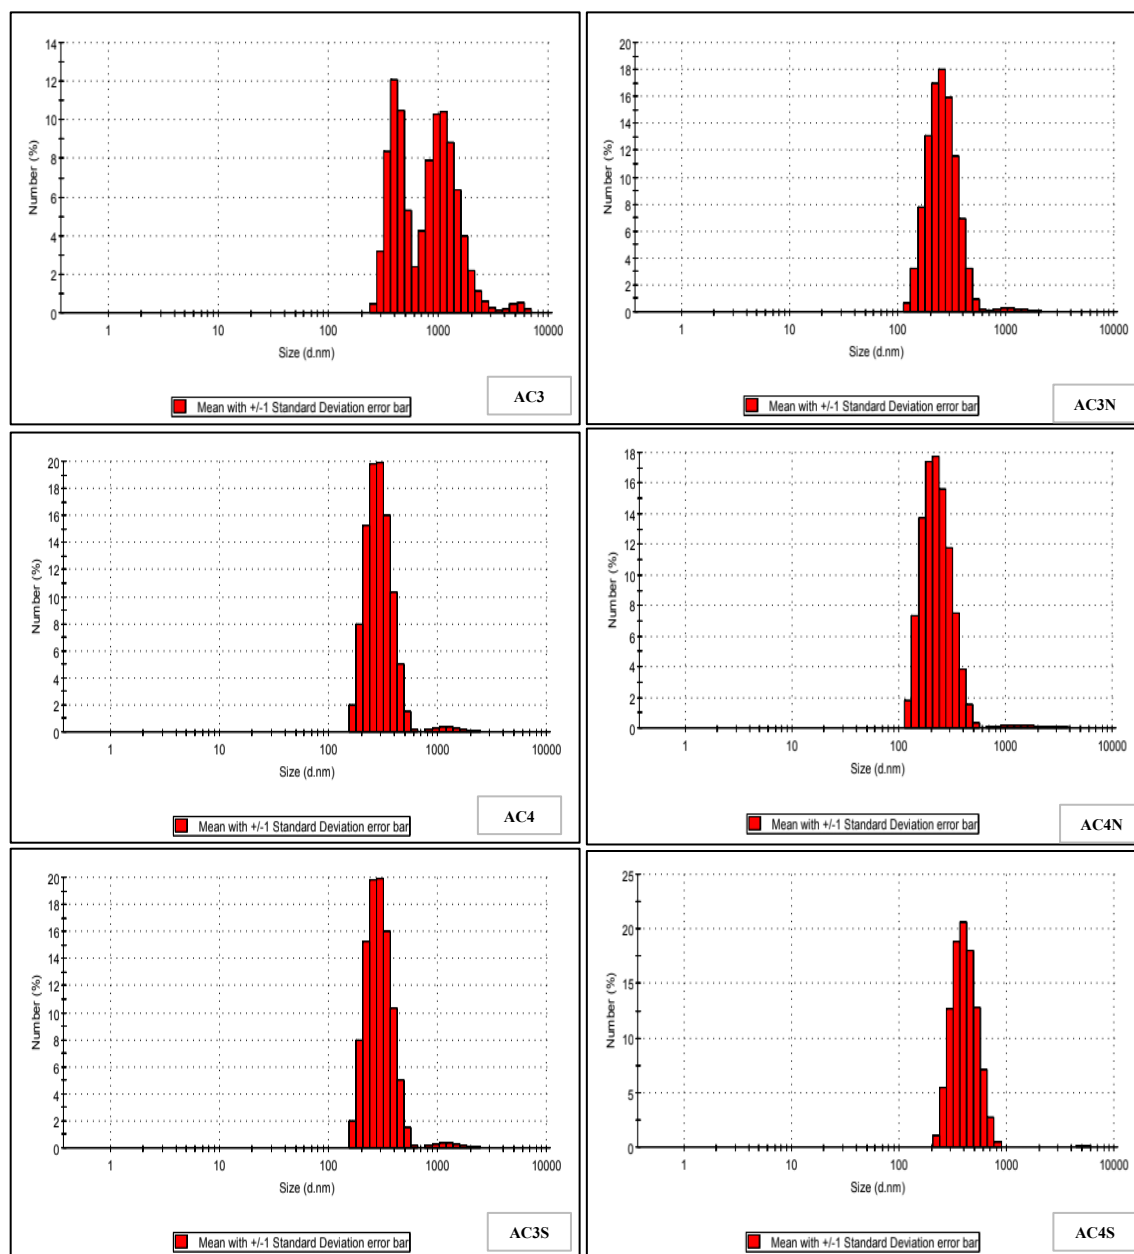


Fig. 5 Particle size analysis graphs of original and modified AC3 and AC4 activated carbons.

These results demonstrate that nitric acid modification led to a reduction in the average particle size distribution of both adsorbents. The values for AC3N and AC4N were determined to be 279.04 and 252.81 nm, respectively. The calculated initial particle size distribution for AC3 at 939.94 nm increased to 992.81 nm in the AC3S sample due to the effect of sulfonic acid modification. Additionally, approximately 70% of AC3S particle sizes fall within the 825-1106 nm range. AC4S sample also showed a similar increase of 34%, calculated as 417.64 nm. Sulfonic acid modification positively influenced the average particle size, which generally led to an increase in average particle size, while nitric acid modification tended to reduce it.

4. CONCLUSIONS

Activated carbons' specific surface area and active sites, two crucial characteristics significantly impacting their adsorption capacity, may be adjusted using chemical modification techniques. In this study, commercial powdered activated carbons were subjected to modification with nitric acid, chlorosulfonic acid, and their combined treatments, followed by a comprehensive characterization of their structural and surface properties. The key points are summarized below:

- Scanning Electron Microscopy (SEM) analysis demonstrated that nitric acid modification resulted in a smoother, cleaner, and more uniform surface morphology, whereas chlorosulfonic acid treatment did not induce significant morphological alterations.
- Fourier-transform infrared spectroscopy (FTIR) revealed the formation of oxygen-containing functional groups such as carboxyl, carbonyl, and quinone upon nitric acid modification. A new peak at 1993.6 cm^{-1} observed in the AC4S sample confirmed the presence of sulfonic groups (S=O and SO_3H), indicating successful sulfonation via chlorosulfonic acid.
- A substantial increase in surface area was achieved with nitric acid treatment, with the highest enhancement (200%) observed in AC4N. A comparable increase was also noted in AC4S, indicating the effectiveness of both acid treatments in enhancing porosity.
- Double acid modification had a detrimental effect on the porous structure, causing surface area reductions of 39% and 76% in AC1 and AC2, respectively. This decrease is attributed to micropore wall degradation or pore blockage due to the formation of surface oxygenated groups.
- All acid-modified samples exhibited a decrease in pH_{PZC} values, reflecting an increase in surface acidity. Surface acid group concentrations increased up to 0.97 meq/g following nitric acid treatment.
- Chlorosulfonic acid modification significantly broadened the particle size distribution, potentially affecting the adsorptive behavior.
- Overall, the findings suggest that nitric acid and chlorosulfonic acid surface modifications are

effective techniques for enhancing the physicochemical properties of activated carbon. When choosing a modification method for adsorption applications, the target pollutants' unique properties should be considered.

- From an application standpoint, nitric acid modification is more suitable for oxygen-containing (polar) organic pollutants due to the increased abundance of acidic oxygen functional groups. In contrast, sulfonic acid modification is considered particularly effective for dye removal owing to the incorporation of strong sulfonic functional groups.
- A significant limitation of this study is the absence of adsorption experiments with real pollutants, which constrains the direct applicability of the findings. To strengthen the practical relevance and real-world applicability, future studies should incorporate adsorption tests using representative contaminants

Acknowledgments

This study was supported by the Scientific and Technological Research Council of Turkey (Project No: 118Y402).

REFERENCES

- [1] T. Rasheed, K. Rizwan, M. Bilal, F. Sher and H. M. Iqbal. Tailored functional materials as robust candidates to mitigate pesticides in aqueous matrices—a review. *Chemosphere*, 282, 131056, 2021.
- [2] M. Ponnuchamy, A. Kapoor, P. Senthil Kumar, D. V. N. Vo, A. Balakrishnan, M. Mariam Jacob and P. Sivaraman. Sustainable adsorbents for the removal of pesticides from water: a review. *Environmental Chemistry Letters*, 19, 2425–2463, 2021.
- [3] V. B. Lunardi, F. E. Soetaredjo, K. Foe, J. N. Putro, I. G. Wenten, W. Irawaty, ... and S. Ismadji. Pesticide elimination through adsorption by metal-organic framework and their modified forms. *Environmental Nanotechnology, Monitoring & Management*, 17, 100638, 2022.
- [4] I. A. Saleh, N. Zouari and M. A. Al-Ghouti. Removal of pesticides from water and wastewater: Chemical, physical and biological treatment approaches. *Environmental Technology & Innovation*, 19, 101026, 2020.
- [5] T. M. Alsaiibi, I. Abustan, M. A. Ahmad and A. A. Foul. A review: production of activated carbon from agricultural by-products via conventional and microwave heating. *Journal of Chemical Technology & Biotechnology*, 88(7), 1183–1190, 2013.
- [6] H. A. Ahsaine, Z. Anfar, M. Zbair, M. Ezahri and N. El Alem. Adsorptive removal of methylene blue and crystal violet onto micro-mesoporous Zr_2O_3 /activated carbon composite: a joint experimental and statistical modeling considerations. *Journal of Chemistry*, 2018, Article ID.
- [7] Z. Anfar, H. A. Ait Ahsaine, M. Zbair, A. Amedlous, A. Ait El Fakir, A. Jada and N. El Alem. Recent trends on numerical investigations of response surface methodology for pollutants adsorption onto activated carbon materials: A

review. *Critical Reviews in Environmental Science and Technology*, 50(10), 1043–1084, 2020.

[8] P. Chingombe, B. Saha and R. J. Wakeman. Surface modification and characterisation of a coal-based activated carbon. *Carbon*, 43(15), 3132–3143, 2005.

[9] I. Pet, M. N. Sanad, M. Farouz, M. M. ElFaham, A. El-Hussein, M. A. El-Sadek and A. Ioanid. Recent developments in the implementation of activated carbon as heavy metal removal management. *Water Conservation Science and Engineering*, 9(2), 62, 2024.

[10] H. K. Kim, S. J. Kim, H. R. Kim and J. W. Park. Nitric acid modified powdered activated carbon for simultaneous adsorption of lead and phenol in aqueous solution. *Journal of Environmental Chemical Engineering*, 12(6), 11488, 2024.

[11] X. Xu, B. Gao, X. Tan, M. Zhang and Q. Yue. Characterization and mechanisms of metal cations removal by a novel magnetic MnFe_2O_4 /biochar composite. *Bioresource Technology*, 276, 247–253, 2019.

[12] M. Mariana, A. K. HPS, E. M. Mistar, E. B. Yahya, T. Alfatah, M. Danish and M. Amayreh. Recent advances in activated carbon modification techniques for enhanced heavy metal adsorption. *Journal of Water Process Engineering*, 43, 102221, 2021.

[13] E. Wolak and A. Orzechowska-Zięba. Change of the surface and structure of activated carbon as a result of HNO_3 modification. *Adsorption*, 30(2), 121–128, 2024.

[14] X. Lu, J. Jiang, K. Sun, X. Xie and Y. Hu. Surface modification, characterization and adsorptive properties of a coconut activated carbon. *Applied Surface Science*, 258(20), 8247–8252, 2012.

[15] Y. Wang, C. Lin, X. Liu, W. Ren, X. Huang, M. He and W. Ouyang. Efficient removal of acetochlor pesticide from water using magnetic activated carbon: Adsorption performance, mechanism, and regeneration exploration. *Science of the Total Environment*, 778, 146353, 2021.

[16] L. Azeez, S. A. Adebisi, A. L. Adejumo, H. K. Busari, H. K. Aremu, O. A. Olabode and O. Awolola. Adsorptive properties of rod-shaped silver nanoparticles-functionalized biogenic hydroxyapatite for remediating methylene blue and congo red. *Inorganic Chemistry Communications*, 142, 109655, 2022.

[17] C. J. Okorie, T. Ojeyemi, A. Egbemhenghe, M. Q. Ali, E. C. Emenike, K. O. Iwuozor and A. G. Adeniyi. Modification of activated carbon for enhanced treatment of per- and polyfluoroalkyl substances: A focused review. *Remediation Journal*, 34(2), e21777, 2024.

[18] A. N. A. El-Hendawy. Influence of HNO_3 oxidation on the structure and adsorptive properties of corncob-based activated carbon. *Carbon*, 41(4), 713–722, 2003.

[19] L. Tang, S. Zhang, L. Li and J. Chen. Preparation of modified activated carbon from corn stalk and adsorption mechanism study for nitrate removal. *Ecotoxicology and Environmental Safety*, 126, 10–17, 2016.

[20] Y. Gökçe and Z. Aktaş. Nitric acid modification of activated carbon produced from waste tea and adsorption of methylene blue and phenol. *Applied Surface Science*, 313, 352–359, 2014.

[21] J. Valentin-Reyes, R. B. García-Reyes, A. García-González, E. Soto-Regalado and F. Cerino-Córdova. Adsorption mechanisms of hexavalent chromium from

aqueous solutions on modified activated carbons. *Journal of Environmental Management*, 236, 815–822, 2019.

[22] X. Li, J. Qiu, Y. Hu, X. Ren, L. He, N. Zhao, ... and X. Zhao. Characterization and comparison of walnut shells-based activated carbons and their adsorptive properties. *Adsorption Science & Technology*, 38(9–10), 450–463, 2020.

[23] C. Coelho, A. S. Oliveira, M. F. R. Pereira and O. C. Nunes. The influence of activated carbon surface properties on the adsorption of the herbicide molinate and the bio-regeneration of the adsorbent. *Journal of Hazardous Materials*, 138(2), 343–349, 2006.

[24] Q. Li, J. Sun, T. Ren, L. Guo, Z. Yang, Q. Yang and H. Chen. Adsorption mechanism of 2,4-dichlorophenoxyacetic acid onto nitric-acid-modified activated carbon fiber. *Environmental Technology*, 39(7), 895–906, 2018.

[25] P. Su, J. Zhang, J. Tang and C. Zhang. Preparation of nitric acid modified powder activated carbon to remove trace amount of Ni(II) in aqueous solution. *Water Science and Technology*, 80(1), 86–97, 2019.

[26] S. X. Liu, X. Chen, X. Y. Chen, Z. F. Liu and H. L. Wang. Activated carbon with excellent chromium (VI) adsorption performance prepared by acid–base surface modification. *Journal of Hazardous Materials*, 141(1), 315–319, 2007.

[27] W. S. Chen, Y. C. Chen and C. H. Lee. Modified activated carbon for copper ion removal from aqueous solution. *Processes*, 10(1), 150, 2022.

[28] C. Liang, Z. Li and G. Zeng. Recent advances in activated carbon modified for better hydrophobic organic contaminant adsorption: A review. *Environmental Science & Technology*, 44(21), 8267–8271, 2010.

[29] J. J. Alvear-Daza, G. A. Pasquale, J. A. Rengifo-Herrera, G. P. Romanelli and L. R. Pizzio. Mesoporous activated carbon from sunflower shells modified with sulfonic acid groups as solid acid catalyst for itaconic acid esterification. *Catalysis Today*, 372, 51–58, 2021.

[30] M. Goswami and P. Phukan. Enhanced adsorption of cationic dyes using sulfonic acid modified activated carbon. *Journal of Environmental Chemical Engineering*, 5(4), 3508–3517, 2017.

[31] N. Eibisch, R. Schroll, R. Fuß, R. Mikutta, M. Helfrich and H. Flessa. Pyrochars and hydrochars differently alter the sorption of the herbicide isoproturon in an agricultural soil. *Chemosphere*, 119, 155–162, 2015.

[32] M. W. Akhtar, N. M. Gabol, M. A. Memon, A. Shaikh, R. Shahbaz and M. Y. Khan. Synthesis and characterization of adsorbent biochar/ MnFe_2O_4 composite from agricultural residue for wastewater treatment. *ECS Journal of Solid State Science and Technology*, 10(5), 057006, 2021.

[33] D. H. Nguyen, H. N. Tran, H. P. Chao and C. C. Lin. Preparation and characterization of activated carbon from banana peels and removal of heavy metal ions from aqueous solutions. *Water Science and Technology*, 76(9), 2369–2380, 2017.

[34] S. Bose, P. S. Kumar, G. Rangasamy, G. Prasannamedha and S. Kanmani. A review on the applicability of adsorption techniques for remediation of recalcitrant pesticides. *Chemosphere*, 313, 137481, 2023.

- [35] A. Guha, W. J. Lu, T. A. Zawodzinski and D. A. Schiraldi. Surface-modified carbons as platinum catalyst support for PEM fuel cells. *Carbon*, 45, 1506–1517, 2007.
- [36] S. A. Dastgheib, T. Karanfil and W. Cheng. Tailoring activated carbons for enhanced removal of natural organic matter from natural waters. *Carbon*, 42(3), 547–557, 2004.
- [37] X. Ge, X. Ma, Z. Wu, X. Xiao and Y. Yan. Modification of coal-based activated carbon with nitric acid using microwave radiation for adsorption of phenanthrene and naphthalene. *Research on Chemical Intermediates*, 41, 7327–7347, 2015.
- [38] N. Bader, S. Souissi-Najar and A. Ouederni. A controlled nitric acid oxidation of an olive stones-based activated carbon: effect of oxidation time. *Lignocellulose Journal*, 3(1), 22–36, 2014.
- [39] H. T. Ma, V. T. T. Ho, N. B. Pham, L. G. Bach and D. T. Phan. The comparison of surface modification methods of the heavy metals adsorption of activated carbon from rice husk. *Applied Mechanics and Materials*, 876, 91–96, 2018.
- [40] M. F. R. Pereira, S. F. Soares, J. J. Órfão and J. L. Figueiredo. Adsorption of dyes on activated carbons: influence of surface chemical groups. *Carbon*, 41(4), 811–821, 2003.
- [41] J. P. Chen and S. Wu. Acid/base-treated activated carbons: characterization of functional groups and metal adsorptive properties. *Langmuir*, 20(6), 2233–2242, 2004.
- [42] S. Asaoka and T. Yamamoto. Characteristics of phosphate adsorption onto granulated coal ash in seawater. *Marine Pollution Bulletin*, 60(8), 1188–1192, 2010.
- [43] İ. Demiral, C. Samdan and H. Demiral. Enrichment of the surface functional groups of activated carbon by modification method. *Surfaces and Interfaces*, 22, 100873, 2021.
- [44] M. Z. Yavuzarslan. Nar kabuğundan elde edilen aktif karbon ile meyve suyundan pestisit adsorpsiyonu (Master's thesis, Fen Bilimleri Enstitüsü), 2019.
- [45] G. Huang, J. X. Shi and T. A. Langrish. Removal of Cr (VI) from aqueous solution using activated carbon modified with nitric acid. *Chemical Engineering Journal*, 152(2–3), 434–439, 2009.
- [46] A. Zahoor, M. Christy, Y. J. Hwang, Y. R. Lim, P. Kim and K. S. Nahm. Improved electrocatalytic activity of carbon materials by nitrogen doping. *Applied Catalysis B: Environmental*, 147, 633–641, 2014.
- [47] M. S. Islam, B. C. Ang, S. Gharekhani and A. B. M. Afifi. Adsorption capability of activated carbon synthesized from coconut shell. *Carbon Letters*, 20, 1–9, 2016.
- [48] I. A. Schepetkin, A. I. Khlebnikov, S. Y. Ah, S. B. Woo, C. S. Jeong, O. N. Klubachuk and B. S. Kwon. Characterization and biological activities of humic substances from mumie. *Journal of Agricultural and Food Chemistry*, 51(18), 5245–5254, 2003.
- [49] H. ShamsiJazeyi and T. Kaghazchi. Investigation of nitric acid treatment of activated carbon for enhanced aqueous mercury removal. *Journal of Industrial and Engineering Chemistry*, 16(5), 852–858, 2010.
- [50] J. W. Shim, S. J. Park and S. K. Ryu. Effect of modification with HNO₃ and NaOH on metal adsorption by pitch-based activated carbon fibers. *Carbon*, 39(11), 1635–1642, 2001.
- [51] X. Hu, H. Zhang and Z. Sun. Adsorption of low concentration ceftazidime from aqueous solutions using impregnated activated carbon promoted by iron, copper and aluminum. *Applied Surface Science*, 392, 332–341, 2017.
- [52] Ç. Öter and Ö. S. Zorer. Adsorption behaviours of Th(IV) and U(VI) using nitric acid (HNO₃) modified activated carbon: equilibrium, thermodynamic and kinetic studies. *International Journal of Environmental Analytical Chemistry*, 101(14), 1950–1965, 2021.
- [53] A. IkhtiarBakti and P. L. Gareso. Characterization of active carbon prepared from coconuts shells using FTIR, XRD and SEM techniques. *Jurnal Ilmiah Pendidikan Fisika Al-Biruni*, 7, 33–39, 2018.
- [54] Q. Huang, A. S. Schafranski, M. J. Hazlett, Y. Xiao and J. M. Hill. Nitric acid functionalization of petroleum coke to access inherent sulfur. *Catalysts*, 10(2), 259, 2020.
- [55] M. Kamari, S. Shafiee, F. Salimi and C. Karami. Comparison of modified boehmite nanoplatelets and nanowires for dye removal from aqueous solution. *Desalination and Water Treatment*, 161, 304–314, 2019.
- [56] O. Adam, M. Bitschené, G. Torri, F. De Giorgi, P. M. Badot and G. Crini. Studies on adsorption of propiconazole on modified carbons. *Separation and Purification Technology*, 46(1–2), 11–18, 2005.
- [57] S. Yao, J. Zhang, D. Shen, R. Xiao, S. Gu, M. Zhao and J. Liang. Removal of Pb (II) from water by the activated carbon modified by nitric acid under microwave heating. *Journal of Colloid and Interface Science*, 463, 118–127, 2016.
- [58] A. Khelifi, M. C. Almazán-Almazán, M. Pérez-Mendoza, M. Domingo-García, F. J. López-Domingo, L. Temdrara and A. Addoun. Influence of nitric acid concentration on the characteristics of active carbons obtained from a mineral coal. *Fuel Processing Technology*, 91(10), 1338–1344, 2010.
- [59] W. Huang, Y. Zhang, S. Bao, R. Cruz and S. Song. Desalination by capacitive deionization process using nitric acid-modified activated carbon as the electrodes. *Desalination*, 340, 67–72, 2014.
- [60] Yu, C., Fan, X., Yu, L., Bandosz, T. J., Zhao, Z., & Qiu, J. (2013). Adsorptive removal of thiophenic compounds from oils by activated carbon modified with concentrated nitric acid. *Energy & Fuels*, 27(3), 1499–1505.
- [61] E. Partlan. Superfine Powdered Activated Carbon (S-PAC) Coupled with Microfiltration for the Removal of Trace Organics in Drinking Water Treatment (Doctoral dissertation, Clemson University), 2017.
- [62] X. Meng, Y. Wan, K. Feng, H. Kong and T. Liu. Preparation and characteristics of three sorbents from wood chips screening reject (WCSR) modified by nitric acid, phosphoric acid, or sodium hydroxide. *BioResources*, 14(1), 2216–2228, 2019.
- [63] Z. Jiang, Y. Liu, X. Sun, F. Tian, F. Sun, C. Liang and C. Li. Activated carbons chemically modified by concentrated H₂SO₄ for the adsorption of the pollutants from wastewater and the dibenzothiophene from fuel oils. *Langmuir*, 19(3), 731–736, 2003.
- [64] A. E. Vasu. Surface modification of activated carbon for enhancement of nickel (II) adsorption. *Journal of Chemistry*, 5(4), 814–819, 2008.
- [65] A. Dąbrowski, P. Podkościelny, Z. Hubicki and M. Barczak. Adsorption of phenolic compounds by activated carbon—a critical review. *Chemosphere*, 58(8), 1049–1070, 2005.

